

Magnetic structure of heavy fermion Ce_2RhIn_8

Wei Bao, P.G. Pagliuso, J.L. Sarrao, J.D. Thompson and Z. Fisk*
 Los Alamos National Laboratory, Los Alamos, NM 87545

J. W. Lynn

NIST Center for Neutron Research, National Institute of Standards and Technology, Gaithersburg, MD 20899
 (February 1, 2008)

The magnetic structure of the heavy fermion antiferromagnet Ce_2RhIn_8 is determined using neutron diffraction. It is a collinear antiferromagnet with a staggered moment of $0.55(6)\mu_B$ per Ce at 1.6 K, tilted 38° from the tetragonal c axis. In spite of its layered crystal structure, the phases for the magnetic moments are the same as those in the cubic parent antiferromagnet CeIn_3 . This suggests that the cubic CeIn_3 building blocks have a stronger influence on magnetic correlations than intervening layers, which gives the material its apparent two-dimensional lattice structure and renders CeRhIn_5 an incommensurate antiferromagnet.

Superconducting heavy fermion materials belong to a special class of correlated electron systems where unconventional superconductivity may be mediated by magnetic fluctuations [1]. Until recently, there were only five U-based heavy fermion materials showing superconductivity at ambient pressure [2] in addition to the original heavy fermion superconductor CeCu_2Si_2 [3]. Three Ce-based heavy fermion materials isostructural to CeCu_2Si_2 and cubic CeIn_3 become superconductors under pressure. Recently, superconductivity has been discovered in a new structure class of heavy fermion materials with chemical formulas $\text{Ce}M\text{In}_5$. While the $M=\text{Rh}$ member superconducts below 2.1 K under 17kbar [4], the $M=\text{Ir}$ and Co members superconduct below 0.4 K and 2.3 K, respectively, at ambient pressure [5,6]. The high superconducting transition temperatures of the new materials hold the record for heavy fermion superconductors. Thermodynamic and transport measurements at low temperature are consistent with unconventional superconductivity in which there are lines of nodes in the superconducting gap [7].

Because CeIn_3 and $\text{Ce}M\text{In}_5$ belong to the $\text{Ce}_nM_m\text{In}_{3n+2m}$ family of structures, they present a unique opportunity for investigating the influence of systematic structure modifications on the superconducting and magnetic properties [8]. In particular, it is interesting to compare CeIn_3 and CeRhIn_5 , which are the $n=\infty$ and $n=1$ members of the $\text{Ce}_n\text{RhIn}_{3n+2}$ subfamily, and can be viewed as periodic stacking of n -layers of CeIn_3 on a layer of $M\text{In}_2$ [9,10]. Both are antiferromagnetic at ambient pressure with $T_N = 10$ K for CeIn_3 [11] and $T_N = 3.8$ K for CeRhIn_5 [4,12]. Both become superconductors when subjected to pressure [4,13], with the superconducting transition temperature of CeRhIn_5 being one order of magnitude higher than that for CeIn_3 . This raises a fundamental question about the role of the intervening $M\text{In}_2$ layers on both the superconductivity and antiferromagnetism. Our study of Ce_2RhIn_8 , which is the $n=2$ member of this heavy fermion sub-family, is intended to shed light on this question by changing the

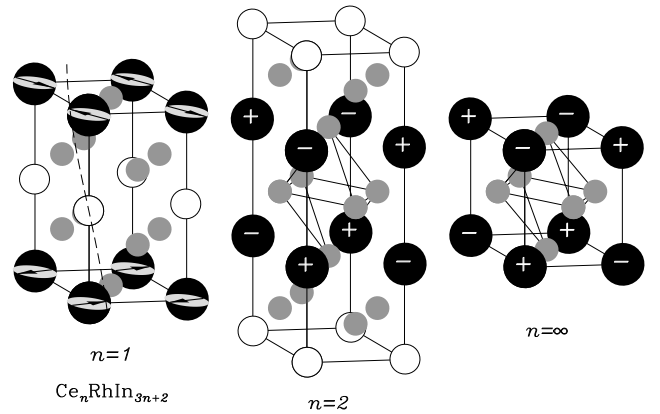


FIG. 1. The magnetic structure of Ce_2RhIn_8 ($n=2$) in a structural unit cell is shown together with CeRhIn_5 ($n=1$) [16] and CeIn_3 ($n=\infty$) [14,15]. The magnetic moment is $0.55\mu_B$ per Ce in Ce_2RhIn_8 and it points 38° from the c axis. The solid circle denotes Ce, the shaded circle In, and the open circle Rh. The disk for CeRhIn_5 denotes the plane in which the ordered moment rotates.

ratio of the CeIn_3 and RhIn_2 layers.

Antiferromagnetic structures for both CeIn_3 and CeRhIn_5 have been determined previously. Cubic CeIn_3 has a simple commensurate magnetic order with wave vector $(1/2, 1/2, 1/2)$ below its Néel temperature. The staggered magnetic moment is $0.48\text{--}0.65\mu_B$ per Ce [14,15]. In contrast, magnetic moments of Ce ions in tetragonal CeRhIn_5 form an incommensurate transverse spiral below $T_N = 3.8$ K, with wave vector $(1/2, 1/2, 0.297)$ [16] (refer to Fig. 1). The staggered moment of $0.37\mu_B$ per Ce at 1.4 K is smaller than that for CeIn_3 . In this paper, we report the magnetic structure for Ce_2RhIn_8 , which orders at $T_N = 2.8$ K [8]. The commensurate antiferromagnetic structure for this $n=2$ material closely resembles that for CeIn_3 ($n=\infty$), rather than the magnetic spiral of CeRhIn_5 ($n=1$). This sug-

TABLE I. Magnetic Bragg intensity, σ_{obs} , defined in Eq. (1), observed at 1.6 K in units of 10^{-3} barns per Ce_2RhIn_8 . The theoretical intensity, σ_{cal} , is calculated using Eq. (2) and (3) with $\beta = 52^\circ$ and $M = 0.55\mu_B/\text{Ce}$.

$\mathbf{q}$	σ_{obs}	σ_{cal}
(0.5 0.5 -1)	52(1)	46.2
(0.5 0.5 0)	0.0(3)	0.0
(0.5 0.5 1)	49(1)	46.2
(0.5 0.5 2)	19(1)	18.9
(0.5 0.5 3)	6.4(4)	5.5
(0.5 0.5 4)	21(1)	23.2
(0.5 0.5 6)	7.5(7)	7.6
(1.5 1.5 0)	0.0(8)	0.0
(1.5 1.5 1)	18(1)	24.8

gests a strong influence of the cubic CeIn_3 structural unit on magnetic correlations in this family of heavy fermion materials.

Single crystals of Ce_2RhIn_8 were grown from an In flux. They crystallize in the tetragonal Ho_2CoGa_8 structure (space group #123, $P4/\text{mmm}$) [9], with lattice parameters $a = 4.665\text{\AA}$ and $c = 12.244\text{\AA}$ at room temperature. The sample used in this study was a well-faceted rectangular plate of dimension $\sim 4 \times 4 \times 0.7$ mm and weight of 88 mg. The largest surface is the (001) plane. Neutron diffraction experiments were performed at NIST using the thermal triple-axis spectrometer BT2 in a two-axis mode. The horizontal collimations were 60-40-40-open. Neutrons with incident energy $E = 35$ meV were selected using the (002) reflection of a pyrolytic graphite (PG) monochromator. The neutron penetration length at this energy is 1.8 mm, which is substantially longer than the thickness of the sample. No rocking-angle dependent absorption was noticed. PG filters of total 9 cm thickness were used to remove higher order neutrons. The sample temperature was regulated by a top loading pumped He cryostat.

Temperature-dependent magnetic Bragg peaks were found at $(m/2, n/2, l)$ with m and n odd integers and l non-zero integers. This corresponds to a magnetic unit cell that doubles the structural unit cell in the basal plane and contains four magnetic Ce ions. Rocking scans at $(1/2, 1/2, 0)$ and $(1/2, 1/2, 1)$, taken at 1.6 K, are shown in Fig. 2(a). The intensity of the $(1/2, 1/2, 1)$ peak is shown in Fig. 2(b) as the square of the order parameter of the magnetic phase transition. Integrated intensities of magnetic Bragg peaks from such rocking scans are normalized to structural Bragg peaks (001), (002), (003), (005), (006) and (220) to yield magnetic scattering cross sections, $\sigma(\mathbf{q}) = I(\mathbf{q}) \sin(\theta_4)$, in absolute units (see Table I). In such units, the magnetic cross section is [17]

$$\sigma(\mathbf{q}) = \left(\frac{\gamma r_0}{2}\right)^2 \langle M \rangle^2 |f(q)|^2 \sum_{\mu, \nu} (\delta_{\mu\nu} - \hat{\mathbf{q}}_\mu \hat{\mathbf{q}}_\nu) \mathcal{F}_\mu^*(\mathbf{q}) \mathcal{F}_\nu(\mathbf{q}), \quad (1)$$

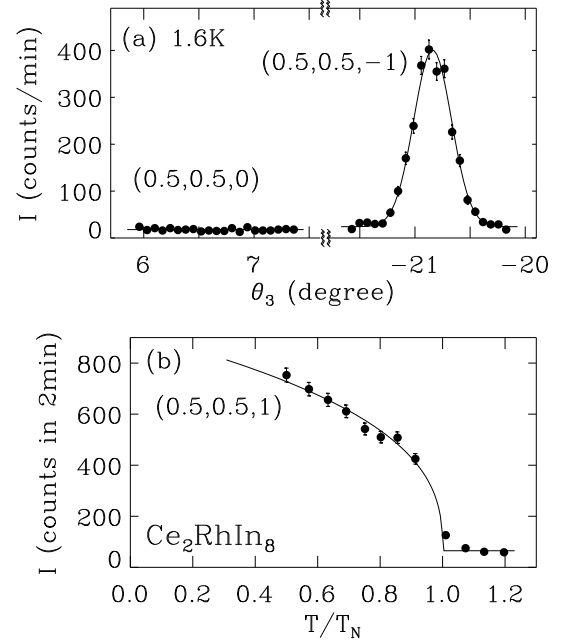


FIG. 2. (a) Elastic rocking scans through magnetic Bragg points $(1/2, 1/2, 0)$ and $(1/2, 1/2, -1)$ at 1.6 K. The $(1/2, 1/2, 0)$ is forbidden for this magnetic structure. (b) Intensity of $(1/2, 1/2, 1)$ as a function of T/T_N . The Néel temperature is 2.8 K.

where $(\gamma r_0/2)^2 = 0.07265$ barns/ μ_B^2 , M is the staggered moment of the Ce ion, $f(q)$ the Ce^{3+} magnetic form factor [18], $\hat{\mathbf{q}}$ the unit vector of $\mathbf{q}$, and $\mathcal{F}_\mu(\mathbf{q})$ the μ th Cartesian component of magnetic structure factor per Ce_2RhIn_8 .

Forbidden peaks at $(m/2, m/2, 0)$ provide an important clue to the magnetic structure of Ce_2RhIn_8 . They could be due to magnetic moments aligning along the $[110]$ direction. However, magnetic twinning in this tetragonal material will yield finite intensities at these reciprocal points. Another, more reasonable, cause is that the nearest-neighbor magnetic moments along the c axis are antiparallel. The phase between the next nearest-neighbor magnetic moments along the c axis and the phases of magnetic moments in a basal layer are already determined by the magnetic wave vector. This yields a collinear antiferromagnetic structure (refer to Fig. 1) with magnetic cross sections per Ce_2RhIn_8

$$\sigma(\mathbf{q}) = 4 \left(\frac{\gamma r_0}{2}\right)^2 \langle M \rangle^2 |f(q)|^2 \langle 1 - (\hat{\mathbf{q}} \cdot \hat{\mathbf{s}})^2 \rangle \sin^2(l\epsilon), \quad (2)$$

where $2\epsilon = 0.38c$ is the separation between the nearest-neighbor Ce ions along the c axis, $\hat{\mathbf{s}}$ is the unit vector of the magnetic moment, and the average, $\langle 1 - (\hat{\mathbf{q}} \cdot \hat{\mathbf{s}})^2 \rangle$, is over magnetic domains.

Fig. 3 shows $\sigma_{obs}(\mathbf{q})/|f(q)|^2 \sim \langle 1 - (\hat{\mathbf{q}} \cdot \hat{\mathbf{s}})^2 \rangle \sin^2(l\epsilon)$

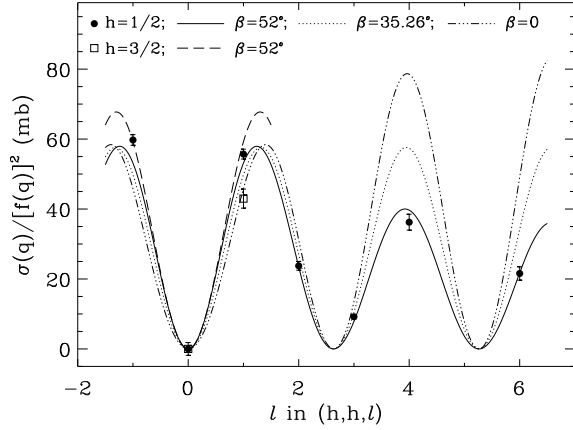


FIG. 3. The l dependence of the magnetic cross-section, σ , divided by the form factor $|f(q)|^2$. The theoretical curves are calculated using Eq. (2) and (3) with $M = 0.55\mu_B$ and various values specified in the figure for the moment tilt angle, β .

as a function of the l index of $\mathbf{q}$. The structure factor, $4\sin^2(l\epsilon)$, not only accounts for the forbidden $l = 0$ magnetic peaks, but it also accounts for the strong oscillation of σ_{obs} as a function of l . The remaining, smooth l dependence is to be accounted for by the polarization factor $\langle 1 - (\hat{\mathbf{q}} \cdot \hat{\mathbf{s}})^2 \rangle$.

Denote the angle between $\mathbf{q}$ and the basal plane as α , and the angle between the basal plane and the magnetic moment as β . Assuming equal occupations among magnetic twins, we have

$$\langle 1 - (\hat{\mathbf{q}} \cdot \hat{\mathbf{s}})^2 \rangle = 1 - \frac{\cos^2 \alpha \cos^2 \beta + 2 \sin^2 \alpha \sin^2 \beta}{2}. \quad (3)$$

For a magnetic moment lying in the basal plane, $\beta = 0$, which is the case for CeRhIn_5 [16,12], the polarization factor varies too much. The resulting theoretical curve does not fit the data (refer to the dot-dashed line in Fig. 3). For $\beta = 35.26^\circ$, which corresponds to $\mathbf{s}$ in the $\langle 111 \rangle$ directions in a cubic system, the polarization factor averages to a constant, $2/3$. The resulting theoretical curve is a better fit (refer to the dotted line in Fig. 3) than that for $\beta = 0$, but it is still not satisfactory. The best least-squares fit (refer to the solid and dashed lines for $h = k = 1/2$ and $h = k = 3/2$ respectively) yields $\beta = 52(2)^\circ$. The staggered magnetic moment is determined at 1.6 K to be $M = 0.55(6)\mu_B$ per Ce.

Having determined the magnetic structure of Ce_2RhIn_8 , now we consider the systematics relating the magnetic structure and lattice structure in $\text{Ce}_n\text{RhIn}_{3n+2}$ (see Fig. 1). In the a - b plane, the magnetic moments of the Ce ions form a square lattice, surrounded by In ions, in all three materials. They all are simple, nearest-neighbor antiferromagnets in the basal plane. In CeRhIn_5 , this Ce antiferromagnetic plane alternates with the RhIn_2 layer. Magnetic correlations across the RhIn_2 layer are incommensurate, with neighboring magnetic moments being rotated

by 107° [16]. The local structure environment in the vertical a - c or the b - c plane within the CeIn_3 double layer in Ce_2RhIn_8 is very similar to that in the basal layer. The same nearest-neighbor antiferromagnetic correlations exist in the double layers. It is interesting that now across the RhIn_2 layer the Ce moments are antiparallel instead of rotated by 107° . The insertion of the RhIn_2 layers between CeIn_3 bilayers, thus, does not modify the magnetic order relative to cubic CeIn_3 . This suggests CeRhIn_5 as a unique member of the $\text{Ce}_n\text{RhIn}_{3n+2}$ family, and the $n \geq 2$ members are likely to be magnetically similar to cubic CeIn_3 . Searching for heavy fermion materials with two-dimensional magnetism seems more profitable if one could find a $\text{Ce}M_m\text{In}_{3+2m}$ structure family, where m MIn_2 layers separate a single CeIn_3 layer.

Another interesting difference between the $n = 1$ and the $n = 2$ materials concerns the magnetic moment orientation. In CeRhIn_5 , the moments rotate in the a - b plane, indicating a XY type magnetic anisotropy. In Ce_2RhIn_8 , the magnetic moments point 52° from the basal plane. Different local anisotropic fields, together with isotropic exchange and crystal fields, likely contribute to the different magnetic structures in the two materials [19]. We also notice that the staggered moment of Ce_2RhIn_8 is comparable to that of CeIn_3 , while T_N of Ce_2RhIn_8 is closer to that of CeRhIn_5 . The $T_N/\langle M \rangle^2$ is the smallest for Ce_2RhIn_8 in the group. Antiferromagnetic transition has been studied in isostructural $\text{Nd}_n\text{MIn}_{3n+2}$ ($M = \text{Rh}, \text{Ir}$ and $n = 1, 2$) and crystal field effects have been emphasized [20]. A detailed understanding of the magnetic interaction in these materials is essential in pursuing magnetic origin of unconventional superconductivity in these heavy fermion metals.

In conclusion, we find the magnetic structure of Ce_2RhIn_8 to be closely related to that of cubic CeIn_3 . The staggered moment is $0.55(6)\mu_B$ per Ce at 1.6 K and it points 52° from the a - b plane. Understanding the different magnetic structures in Ce_2RhIn_8 and CeRhIn_5 may help us understand the enormous enhancement in the superconducting transition temperature of CeRhIn_5 over its cubic relative.

We thank M. E. Zhitomirsky and M. F. Hundley for useful discussions. WB thanks D. C. Dender for technical assistance at NIST. Work at Los Alamos was performed under the auspices of the US Department of Energy. ZF gratefully acknowledges NSF support at FSU. PGP acknowledges FAPESP for partial support.

-
- [1] H. R. Ott and Z. Fisk, in *Handbook on the Physics and Chemistry of Actinides*, eds., A. J. Freeman and G. H. Lander, North-Holland, Amsterdam (1987).
 - [2] R. H. Heffner and M. R. Norman, *Comments Cond. mat. Phys.* **17**, 361 (1996).

- [3] F. Steglich, J. Aarts, C. D. Bredl, W. Lieka, D. Meschede, W. Fraz, and H. Schäfer, Phys. Rev. Lett. **43**, 1982 (1979).
- [4] H. Hegger, C. Petrovic, E.G. Moshopoulou, M.F. Hundley, J.L. Sarrao, Z. Fisk, and J.D. Thompson, Phys. Rev. Lett. **84**, 4986 (2000).
- [5] C. Petrovic, R. Movshovich, M. Jaime, P. G. Pagliuso, M.F. Hundley, J.L. Sarrao, Z. Fisk, and J.D. Thompson, Europhys. Lett. **53**, 354 (2001).
- [6] C. Petrovic, P. G. Pagliuso, M.F. Hundley, R. Movshovich, J.L. Sarrao, J.D. Thompson, Z. Fisk and P. Monthoux, unpublished (2001).
- [7] R. Movshovich, M. Jaime, J.D. Thompson, C. Petrovic, Z. Fisk, P. G. Pagliuso, and J.L. Sarrao, cond-mat/0011365 (2001).
- [8] J.D. Thompson, et al., cond-mat/0012260, to appear in JMMM (2001).
- [9] Yu. N. Grin, et al., Sov. Phys. Crystallogr. **24**, 137 (1979).
- [10] E.G. Moshopoulou, Z. Fisk, J. L. Sarrao and J. D. Thompson, submitted to J. Solid State Chem. (2000).
- [11] K. H. J. Buschow, H. W. de Wijn and A. M. van Diepen, J. Chem. Phys. **50**, 137 (1969).
- [12] N.J. Curro, P.C. Hammel, P.G. Pagliuso, J.L. Sarrao, J.D. Thompson, and Z. Fisk, Phys. Rev. B **62**, R6100 (2000).
- [13] N.D. Mathur, F.M. Grosche, S.R. Julian, I.R. Walker, D.M. Freye, R.K.W. Haselwimmer, and G.G. Lonzarich, Nature **394**, 39 (1998).
- [14] A. Benoit, J.X. Boucherle, P. Convert, J. Flouquet, J. Palleau, and J. Schweizer, Solid State Commun. **34**, 293 (1980).
- [15] J.M. Lawrence and S.M. Shapiro, Phys. Rev. B **22**, 4379 (1980).
- [16] W. Bao, P. G. Pagliuso, J. L. Sarrao, J. D. Thompson, Z. Fisk, J. W. Lynn, and R. W. Erwin, Phys. Rev. B **62**, R14621 (2000).
- [17] G. L. Squires, *Introduction to the Theory of Thermal Neutron Scattering* (Cambridge University Press, Cambridge, 1978).
- [18] M. Blume, A. J. Freeman and R. E. Watson, J. Chem. Phys. **37**, 1245 (1962).
- [19] J. Jensen and A. R. Mackintosh, *Rare Earth Magnetism: Structures and Excitations* (Clarendon Press, Oxford, 1991).
- [20] P. G. Pagliuso, J.D. Thompson, M.F. Hundley, J.L. Sarrao, Phys. Rev. B **62**, 12266 (2000).